

# Metallic materials — Tube — Flattening test

The European Standard EN ISO 8492:2004 has the status of a  
British Standard

ICS 77.040.10

## National foreword

This British Standard is the official English language version of EN ISO 8492:2004. It is identical with ISO 8492:1998. It supersedes BS EN 10233:1994 which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee ISE/NFE/4, Mechanical testing of metals, to Subcommittee ISE/NFE/4/2, Ductility testing, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, page ii, pages 1 and 2, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

### Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 24 November 2004

© BSI 24 November 2004

ISBN 0 580 44851 7

EUROPEAN STANDARD

EN ISO 8492

NORME EUROPÉENNE

EUROPÄISCHE NORM

July 2004

ICS 77.040.10

Supersedes EN 10233:1993

English version

## Metallic materials - Tube - Flattening test (ISO 8492:1998)

Matériaux métalliques - Tubes - Essai d'aplatissement (ISO 8492:1998)

Metallische Werkstoffe - Rohr - Ringfaltversuch (ISO 8492:1998)

This European Standard was approved by CEN on 1 July 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## **Foreword**

The text of ISO 8492:1998 has been prepared by Technical Committee ISO/TC 164 "Mechanical testing of metals" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 8492:2004 by Technical Committee EC/ISS/TC 29 "Steel tubes and fittings for steel tubes", the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

This document supersedes EN 10233:1993.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## **Endorsement notice**

The text of ISO 8492:1998 has been approved by CEN as EN ISO 8492:2004 without any modifications.

INTERNATIONAL  
STANDARD

**ISO**  
**8492**

Second edition  
1998-11-01

---

---

**Metallic materials — Tube — Flattening test**

*Matériaux métalliques — Tubes — Essai d'aplatissement*



Reference number  
ISO 8492:1998(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 8492 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

This second edition cancels and replaces the first edition (ISO 8492:1986), of which it constitutes a technical revision.

# Metallic materials — Tube — Flattening test

## 1 Scope

This International Standard specifies a method for determining the ability of metallic tubes of circular cross-section to undergo plastic deformation by flattening. It may also be used to reveal the defects in the tubes.

This International Standard is applicable to tubes having an outside diameter no greater than 600 mm and a thickness no greater than 15 % of the outside diameter. The range of the outside diameter or thickness, for which this International Standard is applicable may be more exactly specified in the relevant product standard.

## 2 Symbols, designations and units

Symbols, designations and units for the flattening test are given in table 1 and are shown in figure 1.

Table 1

Symbol	Designation	Unit
$a^a$	Wall thickness of the tube	mm
$b$	Inside width of flattened test piece	mm
$D$	Outside diameter of the tube	mm
$H$	Distance between platens measured under load	mm
$L$	Length of the test piece	mm

<sup>a</sup> The symbol  $T$  is also used in steel tube standards.

## 3 Principle

Flattening the end of a tube or a test piece of specified length, cut from a tube in a direction perpendicular to the longitudinal axis of the tube, until the distance between platens measured under load in the direction of flattening reaches a value specified in the relevant product standard [see figure 1, a) and b)].

In the case of close flattening, the internal surfaces of the test piece shall be in contact over at least half of the internal width  $b$  of the flattened test piece standard [see figure 1 c)].

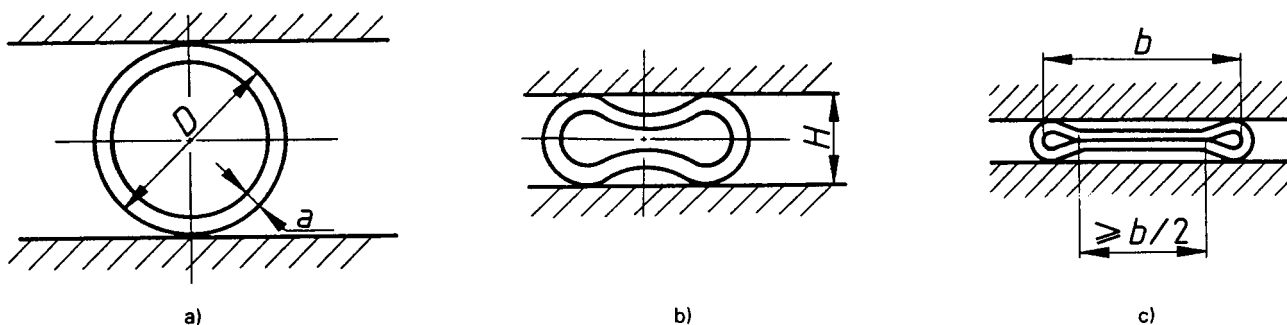


Figure 1

## 4 Testing equipment

**4.1 Test machine**, capable of flattening the test piece to the prescribed distance  $H$  between two plane, parallel, rigid platens.

The width of the platens shall exceed the width of the test piece after flattening i.e. at least  $1,6 D$ , and the length of the platens shall extend over the whole length of the test piece.

## 5 Test piece

**5.1** The length of a test piece shall be no less than 10 mm and no more than 100 mm. The edges of the test piece may be rounded by filing or chamfered by other methods.

NOTE — Non-rounded or non-chamfered edges are permissible if the test result meets the test requirements.

**5.2** When the test is carried out on the end of a full-length tube, the tube shall be cut at right angles to the axis of the tube to a depth of at least 80 % of the tube outside diameter. The cut shall be at a distance from the end of the tube equal to the length of the test piece.

## 6 Procedure

**6.1** In general, the test shall be carried out at ambient temperature within the limits of 10 °C to 35 °C. The test carried out under controlled conditions shall be made at a temperature of  $23\text{ °C} \pm 5\text{ °C}$ .

**6.2** Place the test piece between two platens.

**6.3** Ensure that the weld of the welded tubes is in position as required by the relevant product standard.

**6.4** Flatten the test piece by moving the platens in a direction perpendicular to the longitudinal axis of the tube.

**6.5** In case of dispute, the rate of movement of the platens shall not exceed 25 mm/min.

**6.6** Interpretation of the flattening test shall be carried out in accordance with the requirements of the relevant product standard. When these requirements are not specified, the test piece shall be considered to have passed the test if no cracks are visible without the use of magnifying aids. Slight cracking at the edges shall not be considered cause for rejection.

## 7 Test report

A test report shall be provided when so specified in the relevant product standard. In this case, the test report shall include at least the following information:

- a) reference to this International Standard, i.e. ISO 8492;
- b) identification of the test piece;
- c) dimensions of the test piece;
- d) distance between platens;
- e) position of the weld, if relevant;
- f) result of the test.





---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.  
Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.  
Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.  
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.  
Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).